




Geosynthetic Research Institute

475 Kedron Avenue
Folsom, PA 19033-1208 USA
TEL (610) 522-8440
FAX (610) 522-8441

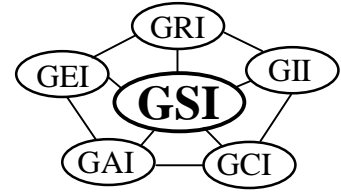

Rev. 6: June 23, 2003
Revision schedule on pg. 14

GRI Test Method GM13*

Standard Specification for

"Test Properties, Testing Frequency and Recommended Warranty for
High Density Polyethylene (HDPE) Smooth and Textured Geomembranes"

This specification was developed by the Geosynthetic Research Institute (GRI), with the cooperation of the member organizations for general use by the public. It is completely optional in this regard and can be superseded by other existing or new specifications on the subject matter in whole or in part. Neither GRI, the Geosynthetic Institute, nor any of its related institutes, warrant or indemnifies any materials produced according to this specification either at this time or in the future.

1. Scope

- 1.1 This specification covers high density polyethylene (HDPE) geomembranes with a formulated sheet density of 0.940 g/ml, or higher, in the thickness range of 0.75 mm (30 mils) to 3.0 mm (120 mils). Both smooth and textured geomembrane surfaces are included.
- 1.2 This specification sets forth a set of minimum, physical, mechanical and chemical properties that must be met, or exceeded by the geomembrane being manufactured. In a few cases a range is specified.
- 1.3 In the context of quality systems and management, this specification represents manufacturing quality control (MQC).

Note 1: Manufacturing quality control represents those actions taken by a manufacturer to ensure that the product represents the stated objective and properties set forth in this specification.

- 1.4 This standard specification is intended to ensure good quality and performance of HDPE geomembranes in general applications, but is possibly not adequate for the complete specification in a specific situation. Additional tests, or more restrictive

*This GRI standard is developed by the Geosynthetic Research Institute through consultation and review by the member organizations. This specification will be reviewed at least every 2-years, or on an as-required basis. In this regard it is subject to change at any time. The most recent revision date is the effective version.

values for test indicated, may be necessary under conditions of a particular application.

- 1.5 This specification also presents a recommended warrant which is focused on the geomembrane material itself.
- 1.6 The recommended warrant attached to this specification does not cover installation considerations which is independent of the manufacturing of the geomembrane.

Note 2: For information on installation techniques, users of this standard are referred to the geosynthetics literature, which is abundant on the subject.

2. Referenced Documents

2.1 ASTM Standards

- D 792 Specific Gravity (Relative Density) and Density of Plastics by Displacement
- D 1004 Test Method for Initial Tear Resistance of Plastics Film and Sheeting
- D 1238 Test Method for Flow Rates of Thermoplastics by Extrusion Plastometer
- D 1505 Test Method for Density of Plastics by the Density-Gradient Technique
- D 1603 Test Method for Carbon Black in Olefin Plastics
- D 3895 Test Method for Oxidative Induction Time of Polyolefins by Thermal Analysis
- D 4218 Test Method for Determination of Carbon Black Content in Polyethylene Compounds by the Muffle-Furnace Technique
- D 4833 Test Method for Index Puncture Resistance of Geotextiles, Geomembranes and Related Products
- D 5199 Test Method for Measuring Nominal Thickness of Geotextiles and Geomembranes
- D 5397 Procedure to Perform a Single Point Notched Constant Tensile Load – (SP-NCTL) Test: Appendix
- D 5596 Test Method for Microscopic Evaluation of the Dispersion of Carbon Black in Polyolefin Geosynthetics
- D 5721 Practice for Air-Oven Aging of Polyolefin Geomembranes
- D 5885 Test method for Oxidative Induction Time of Polyolefin Geosynthetics by High Pressure Differential Scanning Calorimetry
- D 5994 Test Method for Measuring the Core Thickness of Textured Geomembranes
- D 6693 Test Method for Determining Tensile Properties of Nonreinforced Polyethylene and Nonreinforced Flexible Polypropylene Geomembranes

2.2 GRI Standards

- GM10 Specification for the Stress Crack Resistance of Geomembrane Sheet

- GM 11 Accelerated Weathering of Geomembranes using a Fluorescent UVA-Condensation Exposure Device
- GM 12 Measurement of the Asperity Height of Textured Geomembranes Using a Depth Gage

2.3 U. S. Environmental Protection Agency Technical Guidance Document "Quality Control Assurance and Quality Control for Waste Containment Facilities," EPA/600/R-93/182, September 1993, 305 pgs.

3. Definitions

Manufacturing Quality Control (MQC) - A planned system of inspections that is used to directly monitor and control the manufacture of a material which is factory originated. MQC is normally performed by the manufacturer of geosynthetic materials and is necessary to ensure minimum (or maximum) specified values in the manufactured product. MQC refers to measures taken by the manufacturer to determine compliance with the requirements for materials and workmanship as stated in certification documents and contract specifications.

ref. EPA/600/R-93/182

Manufacturing Quality Assurance (MQA) - A planned system of activities that provides assurance that the materials were constructed as specified in the certification documents and contract specifications. MQA includes manufacturing facility inspections, verifications, audits and evaluation of the raw materials (resins and additives) and geosynthetic products to assess the quality of the manufactured materials. MQA refers to measures taken by the MQA organization to determine if the manufacturer is in compliance with the product certification and contract specifications for the project.

ref. EPA/600/R-93/182

Formulation, n - The mixture of a unique combination of ingredients identified by type, properties and quantity. For HDPE polyethylene geomembranes, a formulation is defined as the exact percentages and types of resin(s), additives and carbon black.

4. Material Classification and Formulation

4.1 This specification covers high density polyethylene geomembranes with a formulated sheet density of 0.940 g/ml, or higher. Density can be measured by ASTM D1505 or ASTM D792. If the latter, Method B is recommended.

4.2 The polyethylene resin from which the geomembrane is made will generally be in the density range of 0.932 g/ml or higher, and have a melt index value per ASTM D1238 of less than 1.0 g/10 min.

4.3 The resin shall be virgin material with no more than 10% rework. If rework is used, it must be a similar HDPE as the parent material.

4.4 No post consumer resin (PCR) of any type shall be added to the formulation.

5. Physical, Mechanical and Chemical Property Requirements

5.1 The geomembrane shall conform to the test property requirements prescribed in Tables 1 and 2. Table 1 is for smooth HDPE geomembranes and Table 2 is for single and double sided textured HDPE geomembranes. Each of the tables are given in English and SI (metric) units. The conversion from English to SI (metric) is soft.

Note 3: The tensile strength properties in this specification were originally based on ASTM D 638 which uses a laboratory testing temperature of $23^{\circ}\text{C} \pm 2^{\circ}\text{C}$. Since ASTM Committee D35 on Geosynthetics adopted ASTM D 6693 (in place of D 638), this GRI Specification followed accordingly. The difference is that D 6693 uses a testing temperature of $21^{\circ}\text{C} \pm 2^{\circ}\text{C}$. The numeric values of strength and elongation were not changed in this specification. If a dispute arises in this regard, the original temperature of $23^{\circ}\text{C} \pm 2^{\circ}\text{C}$ should be utilized for testing purposes.

Note 4: There are several tests often included in other HDPE specifications which are omitted from this standard because they are outdated, irrelevant or generate information that is not necessary to evaluate on a routine MQC basis. The following tests have been purposely omitted:

- Volatile Loss
- Dimensional Stability
- Coeff. of Linear Expansion
- Resistance to Soil Burial
- Low Temperature Impact
- ESCR Test (D 1693)
- Wide Width Tensile
- Water Vapor Transmission
- Water Absorption
- Ozone Resistance
- Modulus of Elasticity
- Hydrostatic Resistance
- Tensile Impact
- Field Seam Strength
- Multi-Axial Burst
- Various Toxicity Tests

Note 5: There are several tests which are included in this standard (that are not customarily required in other HDPE specifications) because they are relevant and important in the context of current manufacturing processes. The following tests have been purposely added:

- Oxidative Induction Time
- Oven Aging
- Ultraviolet Resistance
- Asperity Height of Textured Sheet

Note 6: There are other tests in this standard, focused on a particular property, which are updated to current standards. The following are in this category:

- Thickness of Textured Sheet
- Puncture Resistance
- Stress Crack Resistance
- Carbon Black Dispersion (In the viewing and subsequent quantitative interpretation of ASTM D 5596 only near spherical agglomerates shall be included in the assessment).

Note 7: There are several GRI tests currently included in this standard. Since these topics are not covered in ASTM standards, this is necessary. They are the following:

- UV Fluorescent Light Exposure
- Asperity Height Measurement

5.2 The values listed in the tables of this specification are to be interpreted according to the designated test method. In this respect they are neither minimum average roll values (MARV) nor maximum average roll values (MaxARV).

5.3 The properties of the HDPE geomembrane shall be tested at the minimum frequencies shown in Tables 1 and 2. If the specific manufacturer's quality control guide is more stringent and is certified accordingly, it must be followed in like manner.

Note 8: This specification is focused on manufacturing quality control (MQC). Conformance testing and manufacturing quality assurance (MQA) testing are at the discretion of the purchaser and/or quality assurance engineer, respectively.

6. Workmanship and Appearance

6.1 Smooth geomembrane shall have good appearance qualities. It shall be free from such defects that would affect the specified properties of the geomembrane.

6.2 Textured geomembrane shall generally have uniform texturing appearance. It shall be free from agglomerated texturing material and such defects that would affect the specified properties of the geomembrane.

6.3 General manufacturing procedures shall be performed in accordance with the manufacturer's internal quality control guide and/or documents.

7. MQC Sampling

- 7.1 Sampling shall be in accordance with the specific test methods listed in Tables 1 and 2. If no sampling protocol is stipulated in the particular test method, then test specimens shall be taken evenly spaced across the entire roll width.
- 7.2 The number of tests shall be in accordance with the appropriate test methods listed in Tables 1 and 2.
- 7.3 The average of the test results should be calculated per the particular standard cited and compared to the minimum value listed in these tables, hence the values listed are the minimum average values and are designated as "min. ave."

8. MQC Retest and Rejection

- 8.1 If the results of any test do not conform to the requirements of this specification, retesting to determine conformance or rejection should be done in accordance with the manufacturing protocol as set forth in the manufacturer's quality manual.

9. Packaging and Marketing

- 9.1 The geomembrane shall be rolled onto a substantial core or core segments and held firm by dedicated straps/slings, or other suitable means. The rolls must be adequate for safe transportation to the point of delivery, unless otherwise specified in the contract or order.

10. Certification

- 10.1 Upon request of the purchaser in the contract or order, a manufacturer's certification that the material was manufactured and tested in accordance with this specification, together with a report of the test results, shall be furnished at the time of shipment.

11. Warranty

- 11.1 Upon request of the purchaser in the contract or order, a manufacturer's warrant of the quality of the material shall be furnished at the completion of the terms of the contract.
- 11.2 A recommended warranty for smooth and textured HDPE geomembranes manufactured and tested in accordance with this specification is given in Appendix A.
- 11.3 The warranty in Appendix A is for the geomembrane itself. It does not cover subgrade preparation, installation, seaming, or backfilling. These are separate

operations that are often beyond the control, or sphere of influence, of the geomembrane manufacturer.

Note 9: If a warrant is required for installation, it is to be developed between the installation contractor and the party requesting such a document.

Table 1(a) – High Density Polyethylene (HDPE) Geomembrane -Smooth

Properties	Test Method	Test Value							Testing Frequency (minimum)
		30 mils	40 mils	50 mils	60 mils	80 mils	100 mils	120 mils	
Thickness (min. ave.)	D5199	nom.	Nom.	Nom.	Nom.	Nom.	Nom.	Nom.	Per roll
• lowest individual of 10 values		-10%	-10%	-10%	-10%	-10%	-10%	-10%	
Density mg/l (min.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	200,00 lb
Tensile Properties (1) (min. ave.)	D 6693 Type IV	63 lb/in. 114 lb/in.	84 lb/in. 152 lb/in.	105 lb/in. 190 lb/in.	126 lb/in. 228 lb/in.	168 lb/in. 304 lb/in.	210 lb/in. 380 lb/in.	252 lb/in. 456 lb/in.	20,000 lb
• yield strength		12%	12%	12%	12%	12%	12%	12%	
• break strength		700%	700%	700%	700%	700%	700%	700%	
• yield elongation									
• break elongation									
Tear Resistance (min. ave.)	D 1004	21 lb	28 lb	35 lb	42 lb	56 lb	70 lb	84 lb	45,000 lb
Puncture Resistance (min. ave.)	D 4833	54 lb	72 lb	90 lb	108 lb	144 lb	180 lb	216 lb	45,000 lb
Stress Crack Resistance (2)	D5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI-GM10
Carbon Black Content (range)	D 1603 (3)	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	20,000 lb
Carbon Black Dispersion	D 5596	note (4)	note (4)	note (4)	note (4)	note (4)	note (4)	note (4)	45,000 lb
Oxidative Induction Time (OIT) (min. ave.) (5)									200,000 lb
(a) Standard OIT	D 3895	100 min.	100 min.	100 min.	100 min.	100 min.	100 min.	100 min.	
— or —									
(b) High Pressure OIT	D 5885	400 min.	400 min.	400 min.	400 min.	400 min.	400 min.	400 min.	
Oven Aging at 85°C (5), (6)	D 5721								
(a) Standard OIT (min. ave.) - % retained after 90 days	D 3895	55%	55%	55%	55%	55%	55%	55%	per each formulation
— or —									
(b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5885	80%	80%	80%	80%	80%	80%	80%	
UV Resistance (7)	GM 11								
(a) Standard OIT (min. ave.)	D 3895	N.R. (8)	N.R. (8)	N.R. (8)	N.R. (8)	N.R. (8)	N.R. (8)	N.R. (8)	per each formulation
— or —									
(b) High Pressure OIT (min. ave.) - % retained after 1600 hrs (9)	D 5885	50%	50%	50%	50%	50%	50%	50%	

- (1) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction.
Yield elongation is calculated using a gage length of 1.3 inches
Break elongation is calculated using a gage length of 2.0 in.
- (2) The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer’s mean value via MQC testing.
- (3) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.
- (4) Carbon black dispersion (only near spherical agglomerates) for 10 different views:
9 in Categories 1 or 2 and 1 in Category 3
- (5) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.
- (6) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.
- (7) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.
- (8) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.
- (9) UV resistance is based on percent retained value regardless of the original HP-OIT value.

Table 1(b) – High Density Polyethylene (HPDE) Geomembrane - Smooth

Properties	Test Method	Test Value							Testing Frequency (minimum)
		0.75 mm	1.00 mm	1.25 mm	1.50 mm	2.00 mm	2.50 mm	3.00 mm	
Thickness - mils (min. ave.) • lowest individual of 10 values	D5199	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	per roll
Density (min.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	90,000 kg
Tensile Properties (1) (min. ave.) • yield strength • break strength • yield elongation • break elongation	D 6693 Type IV	11 kN/m 20kN/m 12% 700%	15 kN/m 27 kN/m 12% 700%	18 kN/m 33 kN/m 12% 700%	22 kN/m 40 kN/m 12% 700%	29 kN/m 53 kN/m 12% 700%	37 kN/m 67 kN/m 12% 700%	44 kN/m 80 kN/m 12% 700%	9,000 kg
Tear Resistance (min. ave.)	D 1004	93 N	125 N	156 N	187 N	249 N	311 N	374 N	20,000 kg
Puncture Resistance (min. ave.)	D 4833	240 N	320 N	400 N	480 N	640 N	800 N	960 N	20,000 kg
Stress Crack Resistance (2)	D 5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI GM-10
Carbon Black Content - %	D 1603 (3)	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	9,000 kg
Carbon Black Dispersion	D 5596	note (4)	note (4)	note (4)	note (4)	note (4)	note (4)	note (4)	20,000 kg
Oxidative Induction Time (OIT) (min. ave.) (5) (a) Standard OIT — or — (b) High Pressure OIT	D 3895 D 5885	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	90,000 kg
Oven Aging at 85°C (5), (6) (a) Standard OIT (min. ave.) - % retained after 90 days — or — (b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5721 D 3895 D 5885	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	per each formulation
UV Resistance (7) (a) Standard OIT (min. ave.) — or — (b) High Pressure OIT (min. ave.) - % retained after 1600 hrs (9)	D 3895 D 5885	N. R. (8) 50%	N.R. (8) 50%	N.R. (8) 50%	N.R. (8) 50%	N.R. (8) 50%	N.R. (8) 50%	N.R. (8) 50%	per each formulation

(1) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction

Yield elongation is calculated using a gage length of 33 mm

Break elongation is calculated using a gage length of 50 mm

(2) The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.

(3) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(4) Carbon black dispersion (only near spherical agglomerates) for 10 different views:

9 in Categories 1 or 2 and 1 in Category 3

(5) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(6) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(7) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(8) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(9) UV resistance is based on percent retained value regardless of the original HP-OIT value.

Table 2(a) – High Density Polyethylene (HDPE) Geomembrane - Textured

Properties	Test Method	Test Value							Testing Frequency (minimum)
		30 mils	40 mils	50 mils	60 mils	80 mils	100 mils	120 mils	
Thickness mils (min. ave.) • lowest individual for 8 out of 10 values • lowest individual for any of the 10 values	D 5994	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	per roll
Asperity Height mils (min. ave.) (1)	GM 12	10 mil	10 mil	10 mil	10 mil	10 mil	10 mil	10 mil	every 2 nd roll (2)
Density (min. ave.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	200,000 lb
Tensile Properties (min. ave.) (3) • yield strength • break strength • yield elongation • break elongation	D 6693 Type IV	63 lb/in. 45 lb/in. 12% 100%	84 lb/in. 60 lb/in. 12% 100%	105 lb/in. 75 lb/in. 12% 100%	126 lb/in. 90 lb/in. 12% 100%	168 lb/in. 120 lb/in. 12% 100%	210 lb/in. 150 lb/in. 12% 100%	252 lb/in. 180 lb/in. 12% 100%	20,000 lb
Tear Resistance (min. ave.)	D 1004	21 lb	28 lb	35 lb	42 lb	56 lb	70 lb	84 lb	45,000 lb
Puncture Resistance (min. ave.)	D 4833	45 lb	60 lb	75 lb	90 lb	120 lb	150 lb	180 lb	45,000 lb
Stress Crack Resistance (4)	D 5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI GM10
Carbon Black Content (range)	D 1603 (5)	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	20,000 lb
Carbon Black Dispersion	D 5596	note (6)	note (6)	note (6)	note (6)	note (6)	note (6)	note (6)	45,000 lb
Oxidative Induction Time (OIT) (min. ave.) (7) (a) Standard OIT — or — (b) High Pressure OIT	D 3895 D 5885	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	200,000 lb
Oven Aging at 85°C (7), (8) (a) Standard OIT (min. ave.) - % retained after 90 days — or — (b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5721 D 3895 D 5885	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	per each formulation
UV Resistance (9) (a) Standard OIT (min. ave.) — or — (b) High Pressure OIT (min. ave.) - % retained after 1600 hrs (11)	GM11 D 3895 D 5885	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	per each formulation

(1) Of 10 readings; 8 out of 10 must be ≥ 7 mils, and lowest individual reading must be ≥ 5 mils

(2) Alternate the measurement side for double sided textured sheet

(3) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction.

Yield elongation is calculated using a gage length of 1.3 inches

Break elongation is calculated using a gage length of 2.0 inches

(4) P-NCTL test is not appropriate for testing geomembranes with textured or irregular rough surfaces. Test should be conducted on smooth edges of textured rolls or on smooth sheets made from the same formulation as being used for the textured sheet materials.

The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer’s mean value via MQC testing.

(5) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(6) Carbon black dispersion (only near spherical agglomerates) for 10 different views:

9 in Categories 1 or 2 and 1 in Category 3

(7) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(8) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(9) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(10) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(11) UV resistance is based on percent retained value regardless of the original HP-OIT value.

Table 2(b) – High Density Polyethylene (HDPE) Geomembrane - Textured

Properties	Test Method	Test Value							Testing Frequency (minimum)
		0.75 mm	1.00 mm	1.25 mm	1.50 mm	2.00 mm	2.50 mm	3.00 mm	
Thickness mils (min. ave.) • lowest individual for 8 out of 10 values • lowest individual for any of the 10 values	D 5994	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	per roll
Asperity Height mils (min. ave.) (1)	GM 12	0.25 mm	0.25 mm	0.25 mm	0.25 mm	0.25 mm	0.25 mm	0.25 mm	every 2 nd roll (2)
Density (min. ave.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	90,000 kg
Tensile Properties (min. ave.) (3) • yield strength • break strength • yield elongation • break elongation	D 6693 Type IV	11 kN/m 8 kN/m 12% 100%	15 kN/m 10 kN/m 12% 100%	18 kN/m 13 kN/m 12% 100%	22 kN/m 16 kN/m 12% 100%	29 kN/m 21 kN/m 12% 100%	37 kN/m 26 kN/m 12% 100%	44 kN/m 32 kN/m 12% 100%	9,000 kg
Tear Resistance (min. ave.)	D 1004	93 N	125 N	156 N	187 N	249 N	311 N	374 N	20,000 kg
Puncture Resistance (min. ave.)	D 4833	200N	267 N	333 N	400 N	534 N	667 N	800 N	20,000 kg
Stress Crack Resistance (4)	D 5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI GM10
Carbon Black Content (range)	D 1603 (5)	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	9,000 kg
Carbon Black Dispersion	D 5596	note (6)	note (6)	note (6)	note (6)	note (6)	note (6)	note (6)	20,000 kg
Oxidative Induction Time (OIT) (min. ave.) (7) (a) Standard OIT — or — (b) High Pressure OIT	D 3895 D 5885	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	90,000 kg
Oven Aging at 85°C (7), (8) (a) Standard OIT (min. ave.) - % retained after 90 days — or — (b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5721 D 3895 D 5885	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	per each formulation
UV Resistance (9) (a) Standard OIT (min. ave.) — or — (b) High Pressure OIT (min. ave.) - % retained after 1600 hrs (11)	GM11 D 3895 D 5885	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	N.R. (10) 50%	per each formulation

(1) Of 10 readings; 8 out of 10 must be ≥ 0.18 mm, and lowest individual reading must be ≥ 0.13 mm

(2) Alternate the measurement side for double sided textured sheet

(3) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction.

Yield elongation is calculated using a gage length of 33 mm

Break elongation is calculated using a gage length of 50 mm

(4) The SP-NCTL test is not appropriate for testing geomembranes with textured or irregular rough surfaces. Test should be conducted on smooth edges of textured rolls or on smooth sheets made from the same formulation as being used for the textured sheet materials.

The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.

(5) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(6) Carbon black dispersion (only near spherical agglomerates) for 10 different views:
9 in Categories 1 or 2 and 1 in Category 3

(7) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(8) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(9) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(10) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(11) UV resistance is based on percent retained value regardless of the original HP-OIT value.

Appendix “A”

Typical HDPE Geomembrane Warranty

Reviewed by: Donald J. Weiss, Esq.
General Council for GSI

ABC GEOMEMBRANE COMPANY LIMITED WARRANTY

Warranty No: _____
Project No: _____
Effective Date: _____

PURCHASER NAME: _____ PROJECT NAME: _____

ADDRESS: _____ ADDRESS/LOCATION: _____

CITY, STATE, ZIP, COUNTRY _____ CITY, STATE, ZIP, COUNTRY _____

GEOMEMBRANE TYPE/DESCRIPTION _____

ABC Geomembrane Company warrants each ABC geomembrane to be free from manufacturing defects (as defined by the contract's material specifications) and to be able to withstand normal weathering for a period of 5 years from the above effective date for normal use in approved applications.

This Limited Warranty does not include damages or defects in the ABC geomembrane resulting from acts of God, casualty or catastrophe including but not limited to: earthquakes, floods, piercing hail, tornadoes or force majeure. The term "normal use" as used herein does not include, among other things the exposure of ABC geomembranes to harmful chemicals, abuse of ABC geomembranes by machinery, equipment or people; improper site preparation or covering materials, excessive pressures or stresses from any source or improper application or installation. ABC geomembrane material warranty is intended for commercial use only and is not in effect for the consumer as defined in the Magnuson Moss Warranty or any similar federal, state, or local statutes. The parties expressly agree that the sale hereunder is for commercial or industrial use only.

Should defects or premature loss of use within the scope of the above Limited Warranty occur, ABC Geomembrane Company will, at its option, repair or replace the ABC geomembrane on a pro-rata basis at the then current price in such manner as to charge the Purchaser/User only for that portion of the warranted life which has elapsed since purchase of the material. ABC Geomembrane Company will have the right to inspect and determine the cause of any alleged defect in the ABC geomembrane and to take appropriate steps to repair or replace the ABC geomembrane if a defect exists which is covered under this warranty. This Limited Warranty extends only to ABC's geomembrane, and does not extend to the installation service of ABC Geomembrane Company or third parties.

Any claim for any alleged breach of this warranty must be made in writing, by certified mail, to the President of ABC Geomembrane within ten (10) days of becoming aware of the alleged defect. Should the required notice not be given, the defect and all warranties are waived by the Purchaser, and Purchaser shall not have any rights under this warranty. ABC Geomembrane Company shall not be obligated to perform repairs or replacements under this warranty unless and until the area to be repaired or replaced is clean, dry, and unencumbered. This includes, but is not limited to, the area made available for repair and/or replacement of ABC geomembrane to be free from all water, dirt, sludge, residuals and liquids of any kind. If after inspection it is determined that there is no claim under this Limited Warranty, Purchaser shall reimburse ABC Geomembrane Company for its costs associated with the site inspection.

In the event the exclusive remedy provided herein fails in its essential purpose, and in that event only, the Purchaser shall be entitled to a return of the purchase price for so much of the material as ABC Geomembrane Company determines to have violated the warranty provided herein. ABC Geomembrane Company shall not be liable for direct, indirect, special, consequential or incidental damages resulting from a breach of this warranty including, but not limited to, damages for loss of production, lost profits, personal injury or property damage. ABC Geomembrane Company shall not be obligated to reimburse Purchaser for any repairs, replacement, modifications or alterations made by Purchaser unless ABC Geomembrane Company specifically authorized, in writing, said repairs, replacements, modifications or alteration in advance of them having been made. ABC Geomembrane Company's liability under this warranty shall in no event exceed the replacement cost of the material sold to the Purchaser for the particular installation in which it failed.

ABC Geomembrane Company neither assumes nor authorizes any person other than the undersigned of ABC Geomembrane Company to assume for it any other or additional liability in connection with the ABC geomembrane made on the basis of the Limited Warranty. The Limited Warranty on the ABC geomembrane herein is given in lieu of all other possible material warranties, either expressed or implied, and by accepting delivery of the material, Purchaser waives all other possible warranties, except those specifically given.

Limited Warranty is extended to the purchaser/owner and is non-transferable and non-assignable; i.e., there are no third-party beneficiaries to this warranty.

Purchaser acknowledges by acceptance that the Limited Warranty given herein is accepted in preference to any and other possible materials warranties.

ABC GEOMEMBRANE COMPANY MAKES NO WARRANTY OF ANY KIND OTHER THAN THAT GIVEN ABOVE AND HEREBY DISCLAIMS ALL WARRANTIES, BOTH EXPRESSED OR IMPLIED, OF MERCHANTABILITY AND FITNESS FOR A PARTICULAR PURPOSE. THIS IS THE ONLY WARRANTY THAT APPLIES TO THE MATERIALS REFERRED TO HEREIN AND ABC DISCLAIMS ANY LIABILITY FOR ANY WARRANTIES GIVEN BY ANY OTHER PERSON OR ENTITY, EITHER WRITTEN OR ORAL.

ABC GEOMEMBRANE COMPANY'S WARRANTY BECOMES AN OBLIGATION OF ABC GEOMEMBRANE COMPANY TO PERFORM UNDER THE WARRANTY ONLY UPON RECEIPT OF FINAL

I hereby state that I have read and understand the above and foregoing Limited Warranty and agree to such by signing hereunder.

DATE: _____

PURCHASER NAME: _____

ABC GEOMEMBRANE COMPANY: _____
(President or Authorized Representative)

SIGNATURE: _____ DATE _____

SIGNATURE: _____ DATE _____

TITLE: _____

Sworn before me this _____ day of _____ 200 _____

Adoption and Revision Schedule

for

HDPE Specification per GRI-GM13

“Test Properties, Testing Frequency and Recommended Warrant for High Density Polyethylene (HDPE) Smooth and Textured Geomembranes”

- Adopted: June 17, 1997
- Revision 1: November 20, 1998; changed CB dispersion from allowing 2 views to be in Category 3 to requiring all 10 views to be in Category 1 or 2. Also reduced UV percent retained from 60% to 50%.
- Revision 2: April 29, 1999: added to Note 5 after the listing of Carbon Black Dispersion the following: “(In the viewing and subsequent quantitative interpretation of ASTM D5596 only near spherical agglomerates shall be included in the assessment)” and to Note (4) in the property tables.
- Revision 3: June 28, 2000: added a new Section 5.2 that the numeric table values are neither MARV or MaxARV. They are to be interpreted per the the designated test method.
- Revision 4: December 13, 2000: added one Category 3 is allowed for carbon black dispersion. Also, unified terminology to “strength” and “elongation”.
- Revision 5: May 15, 2003: Increased minimum acceptable stress crack resistance time from 200 hrs to 300 hrs.
- Revision 6: June 23, 2003: Adopted ASTM D 6693, in place of ASTM D 638, for tensile strength testing. Also, added Note 2.